

Journal Pre-proof

Ion-exchange mediated removal of cationic dye-stuffs from water using ammonium phosphomolybdate

Jisha Joseph, Raji Chorenjeth Radhakrishnan, Johnly Kannanaikkal Johnson, Steny Pereppadan Joy, Jency Thomas



PII: S0254-0584(19)31300-8

DOI: <https://doi.org/10.1016/j.matchemphys.2019.122488>

Reference: MAC 122488

To appear in: *Materials Chemistry and Physics*

Received Date: 15 August 2019

Revised Date: 25 October 2019

Accepted Date: 25 November 2019


Please cite this article as: J. Joseph, R.C. Radhakrishnan, J.K. Johnson, S.P. Joy, J. Thomas, Ion-exchange mediated removal of cationic dye-stuffs from water using ammonium phosphomolybdate, *Materials Chemistry and Physics* (2019), doi: <https://doi.org/10.1016/j.matchemphys.2019.122488>.

This is a PDF file of an article that has undergone enhancements after acceptance, such as the addition of a cover page and metadata, and formatting for readability, but it is not yet the definitive version of record. This version will undergo additional copyediting, typesetting and review before it is published in its final form, but we are providing this version to give early visibility of the article. Please note that, during the production process, errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

© 2019 Published by Elsevier B.V.

AUTHOR STATEMENT FILE

Author's name	Credit roles
Jisha Joseph	Data collection, Writing-original draft
Raji Chorenjeth Radhakrishnan	Investigation, Formal analysis, Methodology
Johnly Kannanaikkal Johnson	Data collection, Formal analysis
Steny Pereppadan Joy	Data collection, Formal analysis
Jency Thomas	Conceptualization, Supervision, resources, Writing-review and editing

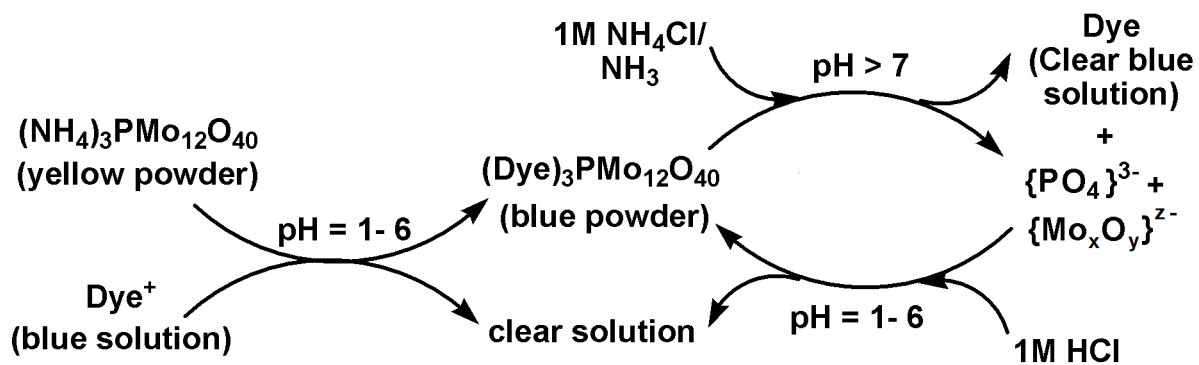

Journal Pre-proof

**Ion-exchange mediated removal of cationic dye-stuffs from water using
ammonium phosphomolybdate**

**Jisha Joseph, Raji Chorenjeth Radhakrishnan, Johnly Kannanaikkal Johnson,
Steny Pereppadan Joy and Jency Thomas***

Centre for Sustainability Science, Research & PG Department of Chemistry, St.

Thomas' College (Autonomous), Thrissur, Kerala-680001, India

* Corresponding author: jencythomas@stthomas.ac.in

Tel: +91-487-2420435; Fax: +91-487-2421510

Abstract

Composition and morphology of micro-sized ammonium phosphomolybdate (APM) particles synthesized under ambient conditions was established using powder X-ray diffraction, fourier transform infrared spectroscopy, thermogravimetric analysis and scanning electron microscopy. Further, the ability of APM particles to remove dye from dye-contaminated water was monitored with respect to nature of incident radiation, concentration, pH and nature of dye. APM could effectively remove cationic dyes from water as long as the pH range permitted the dye to retain its cationic behaviour. This specificity suggested that the removal of dye-stuffs could be attributed to ion-exchange between ammonium ions in APM with cationic dye moieties. APM could be reused several times without affecting its efficiency. Removal efficiency of 94.6% could be retained upto 16th cycle and sensitivity to pH enabled APM to reverse the cation exchange process. The ion-exchange process was not dependent on exposure of APM particles to irradiation which confirmed that the mode of action of APM was not photocatalytic in nature.

Keywords: Ammonium phosphomolybdate, cationic dyes, pH, ion-exchange.

1. Introduction

Rapid industrialization and increase in population density has resulted in severe contamination of water resources. In particular, water pollution caused by dyes has become a serious threat due to its high toxicity and stability to resist degradation even under extreme conditions. Extensive research over the past few decades has resulted in various dye removal techniques that depend on physical, chemical and biological processes [1-3]. Among these, the techniques that rely on adsorption of dyes have a

major advantage over the other techniques that rely on degradation of dyes because potentially hazardous secondary metabolites can also be generated during degradation of dyes [4]. Conventionally adsorbents such as activated carbon [5], bio-waste [6], zeolites [7] and clay materials [8] have been used to treat dye-contaminated water but they suffer from low adsorption capacity and poor selectivity. Therefore, there has been a constant effort in developing new materials that can effectively remove dye moieties from water.

For the past few years, our group has been involved in the synthesis of porous and functionalized phosphomolybdate (PMO) cluster based solids [9-11]. Owing to structural features such as large surface area, porosity, tuneable shape and size; these solids have been explored for potential applications in areas of catalysis, electrical conductivity, luminescence, magnetism, non-linear optics and as anti-tumour agents [12-15]. Among these, ammonium phosphomolybdate (APM), $(\text{NH}_4)_3\{\text{PMo}_{12}\text{O}_{40}\} \cdot x\text{H}_2\text{O}$ is a versatile PMO cluster based solid which was first synthesized by Berzelius in 1826 [16]. Although it has been used as electrode material, catalyst and adsorbent [17-19]; the ion-exchange behavior of APM for the removal of dye-stuffs from water has not been reported so far. Therefore, in the present study, four dyes *viz.* Methylene Blue, Eosin Y, Malachite Green and Methyl Red were selected and their solution was treated with APM. The removal of dye-stuffs was monitored with respect to the change in intensity of its absorbance peak using UV-Visible spectroscopy. Effect of variables such as nature, concentration and pH of dye-stuffs was further investigated and a plausible mechanism for the action of APM on dye-stuffs has been proposed.

2. Experimental

2.1. Synthesis of ammonium phosphomolybdate

All reagents were of reagent grade and were used as received from commercial sources without further purification. Initially, two solutions were prepared. Solution A was prepared by mixing 11.05 g of ammonium heptamolybdate, $(\text{NH}_4)_6\text{Mo}_7\text{O}_{24}\cdot 4\text{H}_2\text{O}$ with 15 mL of ammonia solution and 10 mL of distilled water. The solution was boiled and made up to 250 mL. Secondly, 40 mL of 0.067 M solution of $\text{Na}_2\text{HPO}_4\cdot 12\text{H}_2\text{O}$ (disodium hydrogen phosphate dodecahydrate) was mixed with 20 mL of conc. HNO_3 and was labelled as solution B. Subsequently 100 mL of Solution A was added to Solution B and stirred for 10 minutes. The resultant solution was kept undisturbed for 18 hours and the precipitate formed was allowed to settle down. Finally, it was filtered and the canary yellow precipitate of APM thus obtained was washed with water and air-dried.

2.2. Synthesis of dye solutions

10^{-4} M stock solutions of Methylene Blue (MB), Eosin Y (EY), Malachite Green (MG) and Methyl Red (MR) were prepared by dissolving definite amount of dye in distilled water. The stock solutions were further diluted to 10^{-5} M for the present study.

2.3. Treatment of dye-contaminated water

MB, EY, MG and MR show absorbance peak between 650-700 nm, 500-550 nm, 600-650 nm and 500-550 nm respectively [20-23]. Initially, 25 mL of 10^{-5} M MB solution was taken and its pH was adjusted to 5.0 ± 0.1 using 1M HCl. Subsequently, 0.125 g of APM was added to it and the mixture was kept under stirring for 5 minutes. Thereafter it was left undisturbed for 1 hour. Finally, the MB solution was centrifuged and the filtrate was analyzed using UV-Visible spectroscopy. The absence of absorbance peak at $\lambda_{\text{max}} = 660$ nm indicated that MB had been removed from the solution. Based on the

result obtained (discussed later), the effect of various factors such as contact time, pH, nature of dye and amount of APM was further investigated.

3. Characterization

3.1. Characterization of APM particles

Fourier transform infrared (FTIR) spectrum was recorded on KBr pellets using Shimadzu FTIR spectrophotometer (model: IR Affinity). Before recording the FTIR spectrum, the sample was heated at 120°C for 1 hour. Thermogravimetric analysis (TGA) was done on Perkin-Elmer TGA7 from room temperature to 700°C at a heating rate of 10°C/min in nitrogen atmosphere to determine water content and overall thermal stability of the product. Scanning electron microscopic studies (SEM) were carried out on as-synthesized APM powder mounted on carbon tape using FEI FESEM Quanta 200 at an accelerating voltage of 10 kV. Powder X-ray diffraction (PXRD) data was collected on a Malvern Panalytical Aeris diffractometer using Ni-filtered Cu K α radiation. Data was collected with a step size of 0.02° and count time of 2 s per step over the range 5° < 2 θ < 60°. Nitrogen adsorption and desorption (BELSORP-mini II machine, BEL Japan Inc., Japan) was employed to characterize and measure the pore volume. Before the nitrogen adsorption-desorption measurement, the sample was thoroughly dried at 150°C under vacuum for two hours.

3.2. Removal of dye-stuffs from contaminated water

The removal of dye-stuffs was monitored with respect to change in the intensity of the absorbance peaks using UV-Visible spectroscopy (Shimadzu UV-Visible 1800 double beam spectrophotometer).

The dye removal efficiency of APM was calculated by

$$\text{Removal efficiency (\%)} = \frac{(C_i - C_f)}{C_i} \times 100$$

where, C_i and C_f concentration of dye before and after the treatment with APM [24].

4. Results and Discussion


4.1. Characterization of APM particles

The PXRD pattern of APM particles was found to match well with JCPDS file no. 43-0315 indicating the formation of single-phasic cubic $(\text{NH}_4)_3\text{PMo}_{12}\text{O}_{40}\cdot x\text{H}_2\text{O}$ having lattice constant $a = 11.67 \text{ \AA}$ (Figure 1a). FTIR spectrum (Figure 1b) showed the presence of bands in the region $1100\text{-}700 \text{ cm}^{-1}$ which are characteristic of Keggin type heteropoly anions [25]. The spectrum also showed four FTIR bands at 1067, 964, 869 and 788 cm^{-1} that could be attributed to P-O and Mo-O stretching respectively. Bands at 3212 and 1407 cm^{-1} were assigned as N-H stretching and N-H bending respectively due to the absorption of NH_4^+ ions [26].

The morphology and dimension of APM particles was characterized by SEM. SEM image of APM showed the formation of agglomerated particles having plane faces with diameter $4.5\text{-}9 \mu\text{m}$ (Figure 1c). Figure 1d shows the TGA thermogram obtained by heating as-synthesized APM, $(\text{NH}_4)_3\text{PMo}_{12}\text{O}_{40}\cdot x\text{H}_2\text{O}$ at $10^\circ\text{C}/\text{min}$ from room temperature to 700°C . Two weight loss steps were observed. The initial weight loss of $\sim 5.4\%$ upto 120°C could be attributed to the dehydration of the as-synthesized APM, $(\text{NH}_4)_3\text{PMo}_{12}\text{O}_{40}\cdot x\text{H}_2\text{O}$ wherein x was found to be 6. The value was in good agreement with theoretical value (5.44%) for weight loss corresponding to six molecules of water of crystallization.



The second weight loss of $\sim 4.1\%$ between $120\text{-}500^\circ\text{C}$ indicated the decomposition of the Keggin anion and the evolution of constitutional water together with ammonia gas according to



The second weight loss (4.1%) was also found to be in good agreement with the theoretical value (4.15%) and the values reported earlier in literature [27-29].

4.2. Treatment of dye contaminated water

4.2.1. Effect of nature of light

Initially, 25 mL each of 10^{-5} M Methylene Blue (MB) dye solution having pH = 5.0 ± 0.1 was taken in three beakers. 0.125 g of APM was added to each of the beakers; the solutions were stirred for 5 minutes and kept undisturbed for 1 hour under the following conditions:

- I) The first beaker was kept in dark.
- II) The second beaker was kept in sunlight.
- III) The third beaker was kept under UV light.

The above solutions were centrifuged after 1 hour and filtered. The filtrate was analyzed using UV-Visible spectroscopy. The absence of absorbance peak at $\lambda_{\text{max}} = 660$ nm indicated that MB had been removed from each of the beakers (Figure 2, also refer Table S1, supporting information). The maximum dye removal efficiency of APM was found to be 94.6%. It was also observed that the colour of APM collected from beakers kept in dark, sunlight and UV light had changed from yellow to green after treatment with MB solution. A comparison of PXRD pattern of APM before and after treatment with MB solution confirmed that there were no structural changes in APM upon treatment with MB (Figure S1). The above experiment also indicated that the mode of action of APM was not photocatalytic in nature

4.2.2. Effect of contact time

25 mL each of 10^{-5} M MB dye solution having $\text{pH} = 5.0 \pm 0.1$ was taken in five beakers. 0.125 g of APM was added to each of the beakers and the solutions were stirred for 5 minutes. The solutions were left undisturbed and centrifuged after different time intervals (0, 15, 30, 45 and 60 minutes). Subsequently, the filtrate from each beaker was monitored using UV-Visible spectroscopy (Figure 3). From Figure 3 it is evident that the removal of MB (removal efficiency = 94.6%) takes place instantaneously i.e. as soon as the dye comes in contact with APM (also refer Table S2).

4.2.3. Effect of amount of APM

25 mL each of 10^{-5} M MB dye solution having $\text{pH} = 5.0 \pm 0.1$ was taken in five beakers and a definite amount of APM was added to each of the beakers. The solutions were stirred for 5 minutes and centrifuged. From UV-Visible spectroscopy (Figure 4) it was evident that the maximum removal efficiency (i.e. 94.6%) was obtained within 5 minutes of stirring when 25 mL of 10^{-5} M MB dye solution was treated with 0.125 g of APM.

4.2.4. Effect of nature of dye

In order to investigate the nature of dye, four different dyes *viz.* MB, EY, MG and MR were selected. 25 mL of 10^{-5} M solution of each dye (having $\text{pH} = 5.0 \pm 0.1$) was treated with 0.125 g of APM. The solutions were stirred for 5 minutes and centrifuged. In all the cases, the filtrate was analyzed using UV-Visible spectroscopy. The spectra indicated that MB, MR and MG had been removed from dye-contaminated water upon treatment with APM. The absence of absorbance peak between 650-700 nm, 500-550 nm and 600-650 nm respectively confirmed the removal of dye-stuffs from water (Figure 5). However, in the case of EY there was no significant change in the

absorbance peak before and after treatment with APM. The result suggested that APM was effective only for the removal of cationic dyes from water.

4.2.5. Influence of pH

25 mL each of 10^{-5} M MR, MG and MB solution was taken and its pH was adjusted between 1.0 ± 0.1 to 6 ± 0.1 using 1M HCl. The resultant dye solutions were treated with 0.125 g of APM. The investigations revealed that APM could effectively remove MB and MG from dye-contaminated water in the pH range 1-6. This could be attributed to the cationic nature of MB and MG in the pH range 1-6 (Figure S2). However, APM could not remove MR from solution at pH above 5 (Figure 6). A preview of literature suggested that MR exists as anionic dye at pH above 5 [21]. A similar result was obtained in the case of EY. EY exists either as a neutral or an anionic dye in the pH range 1-6 [22]. Therefore, there was no significant change in its absorbance peak before and after treatment with APM. The results suggested that perhaps ion-exchange of ammonium ions in APM with cationic dye moieties is responsible for the removal of dye-stuffs.

4.2.6. Reusability of APM

The reusability of APM for the removal of MB was analyzed for 20 cycles using 25 mL of 10^{-5} M dye solution having pH = 5.0 ± 0.1 . In the first cycle, 0.125 g of APM was added to MB solution, stirred for 5 minutes and centrifuged. APM thus obtained was air-dried and subsequently treated with 25 mL of 10^{-5} M dye solution having pH = 5.0 ± 0.1 and this process was repeated for 20 cycles. The removal of MB was observed upto 16th cycles (Table S3) wherein 94.6% removal efficiency was achieved. However, the contact time required to remove MB from dye-contaminated water increased with subsequent number of cycles. While only 5 minutes of stirring was required upto 4th

cycle, 10 minutes of stirring was required upto 8th cycle to achieve the removal efficiency of 94.6%. Therefore, the time of stirring was gradually increased 5 minutes per four cycles.

4.2.7. Adsorption capacity of APM

The adsorption/desorption isotherm of APM, resembles that of Brunauer's Type I isotherm, that is the characteristic for microporous adsorbents (Figure 7) [30]. The microporosity was confirmed from the mean pore diameter of 1.8158 nm obtained from BET plot. Further, the total pore volume of APM was estimated to confirm whether dye moieties could be adsorbed in the micro pores of APM. It was observed that pore volume had reduced from 8.013×10^{-2} to $3.0306 \times 10^{-2} \text{ cm}^3/\text{g}$ after APM had been treated with MB solutions for 16 cycles. The decrease in total pore volume confirmed the presence of MB moieties in the micropores of APM (refer Table 1 for textural parameters of APM before and after the treatment of dye-stuffs).

4.3. Mechanism

Based on the above observations it was evident that the presence of NH_4^+ ions in APM facilitates ion-exchange between NH_4^+ ions and cationic dye moieties. A preview of literature suggests that APM is an excellent adsorbent and it can adsorb metal ions such as Cs^+ , K^+ , Na^+ , Sn^{2+} , Bi^{3+} etc. via ion-exchange between NH_4^+ ions and metal ions [31-34]. Therefore, a similar mechanism has been proposed herein. The removal of cationic dye-stuffs may be visualized as an ion-exchange process between NH_4^+ ions and cationic dye moieties. This was confirmed by comparing the PXRD pattern of APM obtained after 16 cycles of treatment with MB with PXRD pattern of as-synthesized APM particles (Figure S3). The PXRD pattern indicated that APM does not undergo any structural changes upon treatment with MB but rather it facilitates an ion-exchange

between NH_4^+ ions and cationic dye moieties. It is noteworthy that the sensitivity to pH enabled APM to reverse the cation exchange process.

APM is stable only in acidic medium ($\text{pH} \leq 6$) [35]. At $\text{pH} > 6$, it disintegrates into its soluble molecular precursors i.e. NH_4^+ , $\{\text{PO}_4\}^{3-}$ and $\{\text{Mo}_x\text{O}_y\}^z$ ions [36]. Therefore, the present investigation was carried out at $\text{pH} \leq 6$. At $\text{pH} = 1-6$, cationic dyes readily replace NH_4^+ ions in APM to form $(\text{Dye})_3\text{PMo}_{12}\text{O}_{40}$. Interestingly, the ion-exchanged dye moieties could be regenerated in solution when APM was treated with 10 ml of 1M NH_4Cl and 0.5 ml of NH_3 (Figure 8). However, the addition of $\text{NH}_4\text{Cl}/\text{NH}_3$ solution increased the pH of the medium ($\text{pH} > 7$) and two outcomes were observed:

(a) In the case of MR, at $\text{pH} > 7$ a clear yellow solution (**V**, refer Figure 8a) was observed due to disintegration of APM and change in color of MR into yellow. Upon adjusting the pH of the solution **V** using 1M HCl i.e. at $\text{pH} = 5-6$, APM and MR could be regenerated and separated by centrifugation and filtration.

(b) In the case of MB and MG, at $\text{pH} > 7$ $(\text{Dye})_3\text{PMo}_{12}\text{O}_{40}$ disintegrates into its soluble molecular precursors i.e. Dye, $\{\text{PO}_4\}^{3-}$ and $\{\text{Mo}_x\text{O}_y\}^z$ moieties resulting in a clear blue solution **V** (refer Figure 8b). However, upon addition of 1M HCl, pH of the solution was adjusted between 1-6 wherein APM and dye could be regenerated as $(\text{Dye})_3\text{PMo}_{12}\text{O}_{40}$ i.e. residue **IV**.

5. Conclusions

Micro-sized ammonium phosphomolybdate, $(\text{NH}_4)_3\text{PMo}_{12}\text{O}_{40} \cdot 6\text{H}_2\text{O}$ particles were synthesized under ambient conditions and characterized. APM was found to be an effective medium for the removal of cationic dyes in acidic medium. While Methylene Blue and Malachite Green could be eliminated from dye-contaminated water in the pH range 1-6; Methyl Red could be removed only in the pH range 1-5. Dye removal

efficiency as high as 94.6% was achieved upon treating 10^{-5} M MB solution (pH = 5.0 ± 0.1) with APM. APM could be successfully re-used upto 16 cycles. The removal of dye-stuffs from contaminated water could be attributed to ion-exchange between ammonium ions in APM with cationic dye moieties. The ion-exchange process was found to be reversible which enabled APM and dye moieties to be regenerated in solution.

Acknowledgements. JT sincerely acknowledges her mentor Prof. A. Ramanan, Department of Chemistry, Indian Institute of Technology (IIT), Delhi for the guidance and support extended over the years. JT thanks UGC for research project 2243-MRP/15-16/KLCA019/UGC-SWRO. The authors acknowledge DST and UGC for FIST and CPE program respectively implemented in St. Thomas' College (Autonomous), Thrissur.

References

1. V. Katheresan, J. Kannedo, S.Y. Lau, Efficiency of various recent wastewater dye removal methods: A review, *J. Environ. Chem. Eng.* 6 (2018) 4676-4697. <https://doi.org/10.1016/j.jece.2018.06.060>
2. Z. Huang, Y. Li, W. Chen, J. Shi, N. Zhang, X. Wang, Z. Li, L. Gao, Y. Zhang, Modified bentonite adsorption of organic pollutants of dye wastewater, *Mater. Chem. Phys.* 202 (2017) 266-276. <https://doi.org/10.1016/j.matchemphys.2017.09.028>
3. I. Ali, C. Peng, I. Naz, D. Lin, D.P. Saroj, M. Ali, Development and application of novel bio-magnetic membrane capsules for the removal of the cationic dye malachite green in waste water treatment, *RSC Adv.* 9 (2019) 3625-3646. <https://doi.org/10.1039/C8RA09275C>

4. S. Erdemoglu, S.K. Aksu, F. Sayilkan, B. Izgi, M. Asilturk, H. Sayilkan, F. Frimmel, S. Gucer, Photocatalytic degradation of Congo Red by hydrothermally synthesized nanocrystalline TiO₂ and identification of degradation products by LC-MS, *J. Hazard. Mater.* 155 (2008) 469-476.
<https://doi.org/10.1016/j.jhazmat.2007.11.087>
5. L. Liu, Y. Lin, Y. Liu, H. Zhu, Q. He, Removal of Methylene Blue from aqueous solutions by sewage sludge based granular activated carbon: adsorption equilibrium, kinetics, and thermodynamics, *J. Chem. Eng. Data.* 58 (2013) 2248-2253.
<https://doi.org/10.1021/je4003543>
6. V.K. Gupta, A. Mittal, V. Gajbe, J. Mittal, Removal and recovery of the hazardous azo dye Acid Orange 7 through adsorption over waste materials: Bottom ash and de-oiled soya, *Ind. Eng. Chem. Res.* 45 (2006) 1446-1453.
<https://doi.org/10.1021/ie051111f>
7. S. Wang, H. Li, L. Xu, Application of zeolite MCM-22 for basic dye removal from wastewater, *J. Colloid Interface Sci.* 295 (2006) 71-78.
<https://doi.org/10.1016/j.jcis.2005.08.006>
8. A. Kausar, M. Iqbal, A. Javed, K. Aftab, Z. Nazli, H.N. Bhatti, S. Nouren, Dye adsorption using clay and modified clay: A review, *J. Mol. Liq.* 256 (2018) 395-407.
<https://doi.org/10.1016/j.molliq.2018.02.034>
9. J. Thomas, K.R. Kannan, A. Ramanan, Nanostructured phosphomolybdates, *J. Chem. Sci.* 120 (2008) 529-536.
<https://doi.org/10.1007/s12039-008-0082-4>

10. J. Thomas, A. Ramanan, Phosphomolybdate cluster based solids mediated by transition metal complexes, *Inorg. Chim. Acta* 372 (2011) 243-249.
<https://doi.org/10.1016/j.ica.2011.02.028>
11. J. Thomas, D. Kumar, A. Ramanan, Crystallization of phosphomolybdate clusters mediated by copper azole complexes: Influence of pH and temperature, *Inorg. Chim. Acta* 396 (2013) 126-135.
<https://doi.org/10.1016/j.ica.2012.10.034>
12. S. Pathan, A. Patel, Keggin type transition substituted phosphomolybdates: heterogeneous catalysts for selective aerobic oxidation of alcohols and alkenes under solvent free condition, *Catal. Sci. Technol.* 4 (2014) 648-656.
<https://doi.org/10.1039/C3CY00717K>
13. L. Ai, Z. Wang, F. He, Q. Wu, Synthesis and conductive performance of polyoxometalate acid salt gel electrolytes, *RSC Adv.* 8 (2018) 34116-34120.
<https://doi.org/10.1039/C8RA07160H>
14. P. Sun, S. Zhang, Z. Xiang, T. Zhao, D. Sun, G. Zhang, M. Chen, K. Guo, X. Xin, Photoluminescent sensing vesicle platform self-assembled by polyoxometalate and ionic-liquid-type imidazolium gemini surfactants for the detection of Cr^{3+} and MnO_4^- ions, *J. Coll. Inter. Sci.* 547 (2019) 60-68.
<https://doi.org/10.1016/j.jcis.2019.03.085>
15. X. Qu, H. Feng, C. Ma, Y. Yang, X. Yu, Synthesis, crystal structure and antitumor activity of a novel 3D supramolecular compound constructed from Strandberg-type polyoxometalate and benzimidazole, *Inorg. Chem. Commun.* 81 (2017) 22-26.
<https://doi.org/10.1016/j.inoche.2017.04.023>

16. J.J. Berzelius, Ueber die Schwefelsalze, *Annalen der Physik* 83 (1826) 261-288.
<https://doi.org/10.1002/andp.18260830702>
17. S.D. Pandey, P. Tripathi, Investigation of some new solid cation exchange membrane electrodes for activity determination of mon-valent cations, *Electrochim. Acta* 27 (1982) 1715-1721.
[https://doi.org/10.1016/0013-4686\(82\)80168-0](https://doi.org/10.1016/0013-4686(82)80168-0)
18. M. Basu, S. Sarkar, S. Pande, S. Jana, A.K. Sinha, S. Sarkar, M. Pradhan, A. Pal, T. Pal, Hydroxylation of benzophenone with ammonium phosphomolybdate in the solids state via UV photoactivation, *Chem. Commun.* (2009) 7191-7193.
<https://doi.org/10.1016/j.inoche.2017.04.023>
19. S.J. Gregg, R. Stock, The adsorption of hydrocarbon vapours by ammonium phosphomolybdate, *Trans. Faraday Soc.* 53 (1957) 1355-1362.
<https://doi.org/10.1039/TF9575301355>
20. A. Joshi, S. Vaidya, M. Singh, Synthesis and structure of Anderson cluster based organic-inorganic hybrid solid, $[\{Cu(2-pzc)(H_2O)_2\}_2\{H_7AlMo_6O_{24}\}] \cdot 17H_2O$ and its dye adsorption properties, *J. Chem. Sci.* 131 (2019) 1-7.
<https://doi.org/10.1007/s12039-018-1583-4>
21. L. Ayed, A. Mahdhi, A. Cheref, A. Bakhrouf, Decolorization and degradation of azo dye Methyl Red by an isolated *Sphingomonas paucimobilis*: Biototoxicity and metabolites characterization, *Desalination* 274 (2011) 272-277.
<https://doi.org/10.1016/j.desal.2011.02.024>
22. N. Sharma, R. Jha, S. Baghel, D. Sharma, Study on photocatalyst Zinc Oxide annealed at different temperatures for photodegradation of Eosin Y dye, *J. Alloys Compd.* 695 (2017) 270-279.

- <https://doi.org/10.1016/j.jallcom.2016.10.194>
23. N. Chauhan, V. Singh, S. Kumar, M. Kumari, K. Sirohi, Synthesis of nitrogen & palladium co-doped mesoporous titanium dioxide nanoparticles via evaporation induced self assembly method and study of their photocatalytic properties, *J. Mol. Struct.* 1185 (2019) 219-228.
- <https://doi.org/10.1016/j.molstruc.2019.02.055>
24. R. Abbassi, A.K. Yadava, N. Kumar, S. Huanga, P.R. Jaffea, Modeling and optimization of dye removal using “green” clay supported iron nano-particles, *Ecol. Eng.* 61 (2013) 366–370.
- <https://doi.org/10.1016/j.ecoleng.2013.09.040>
25. M. Qi, K. Yu, Z. Su, C. Wang, C. Wang, B. Zhou, C. Zhu, Assembly of four new supramolecular compounds based on Keggin phosphomolybdate and different organocations, *Inorg. Chim. Acta* 400 (2013) 59-66.
- <https://doi.org/10.1016/j.ica.2013.01.030>
26. A. Tadjarodi, A.I. Zad, M. Imani, Mixed ammonium silver phosphomolybdate salt nanostructures; solid state synthesis, characterization of driving agent role and photocatalytic property, *Mater. Lett.* 161 (2015) 464-467.
- <https://doi.org/10.1016/j.matlet.2015.09.002>
27. S. Ilhan, C. Kahruman, I. Yusufoglu, Characterization of the thermal decomposition products of ammonium phosphomolybdate hydrate, *J. Anal. Appl. Pyrolysis.* 78 (2007) 363-370.
- <http://dx.doi.org/10.1016/j.jaap.2006.09.009>

28. L. Dermeche, R. Thouvenot, S. Hocine, C. Rabia, Preparation and characterization of mixed ammonium salts of Keggin phosphomolybdate, *Inorg. Chim. Acta* 362 (2009) 3896-3900
<https://doi.org/10.1016/j.ica.2009.04.049>
29. B.M. Abu-Zied, A.A.A. Farrag, A.M. Asiri, Preparation of caesium-substituted phosphomolybdic acid via solid-state ion exchange method, *Powder Technol.* 246 (2013) 643-649.
<https://doi.org/10.1016/j.powtec.2013.06.004>
30. S. Lowell, J.E. Shields, Powder surface area and porosity, *Adsorption isotherms* (1984) 11-13.
https://doi.org/10.1007/978-94-009-5562-2_3
31. H.R. Ghalebi, S. Aber, A. Karimi, Keggin type of cesium phosphomolybdate synthesized via solid-state reaction as an efficient catalyst for the photodegradation of a dye pollutant in aqueous phase, *J. Mol. Catal. A: Chem.* 415 (2016) 96-103.
<http://dx.doi.org/10.1016/j.molcata.2016.01.031>
32. J.V.R. Smit, Ammonium salts of the heteropolyacids as cation exchangers, *Nature* 181 (1958) 1530-1531.
<https://doi.org/10.1038/1811530a0>
33. Y. Park, W.S. Shin, S.J. Choi, Ammonium salt of heteropoly acid immobilized on mesoporous silica (SBA-15): An efficient ion exchanger for cesium ion, *Chem. Eng. J.* 220 (2013) 204-213.
<https://doi.org/10.1016/j.cej.2013.01.027>

34. C.J. Coetzee, E.F.C.H. Rohwer, The determination of sodium and potassium after separation from each other and other ions by means of ammonium phosphomolybdate and other ion exchangers, *Anal. Chim. Acta* 44 (1969) 293-299.
[https://doi.org/10.1016/S0003-2670\(01\)95802-7](https://doi.org/10.1016/S0003-2670(01)95802-7)
35. J. Thomas, A. Ramanan, Growth of copper pyrazole complex templated phosphomolybdates: supramolecular interactions dictate nucleation of a crystal, *Cryst. Growth Des.* 8 (2008) 3390-3400.
<https://doi.org/10.1021/cg800344h>
36. J. Alcaniz-Monge, G. Trautwein, M.C. Roman-Martinez, Effect of counteranion of ammonium salts on the synthesis of porous nanoparticles $(\text{NH}_4)_3[\text{PMo}_{12}\text{O}_{40}]$, *Solid State Sci.* 13 (2011) 30-37.
<https://doi.org/10.1016/j.solidstatesciences.2010.10.002>

Table 1. Textural parameters of APM before (I) and after (II) the treatment of dye-stuffs.

S. No.	Textural parameter	I	II
1	Total pore volume ($p/p^0=0.990$) [cm^3/g]	8.0131×10^{-2}	3.0306×10^{-2}
2	Surface area (BET) [m^2/g]	1.7652×10^2	44.512

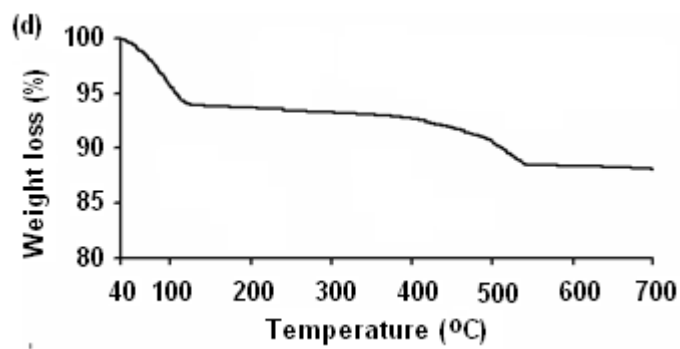
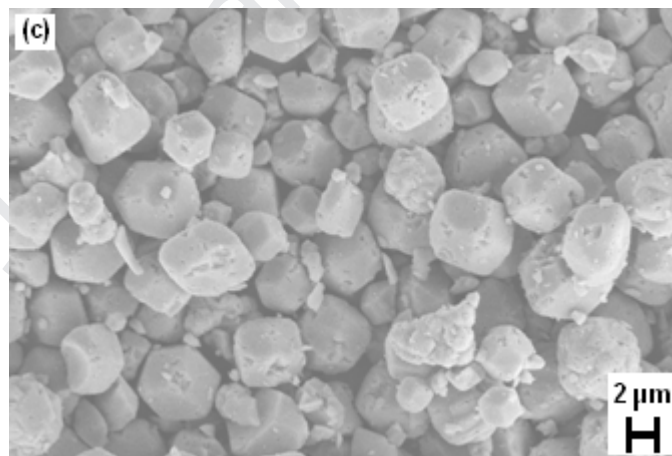
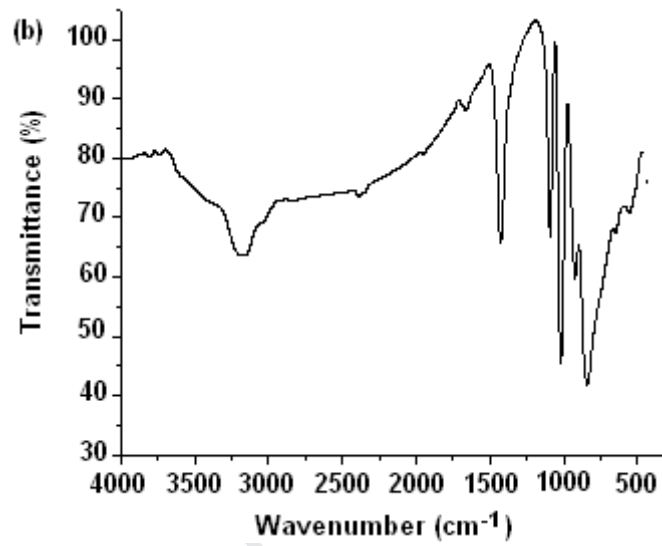
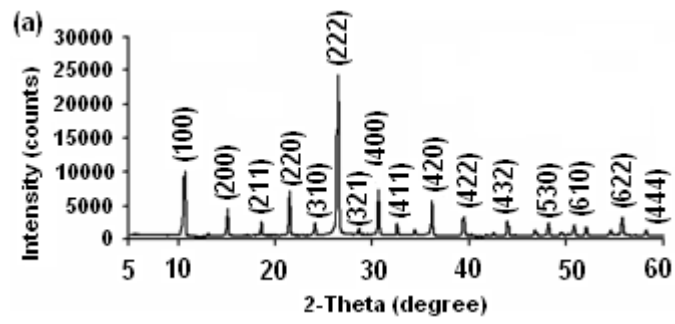


Figure 1. (a) Indexed PXRD pattern (b) FTIR spectrum (c) SEM image and (d) TGA curve of as-synthesized APM particles.

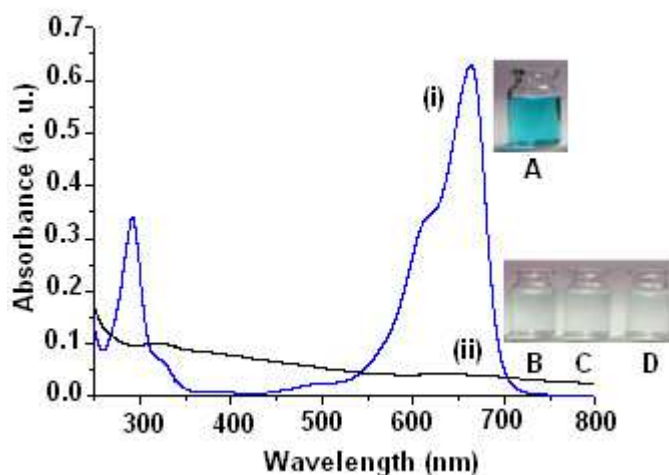


Figure 2. Figure showing UV-Visible spectra of (i) original solution of Methylene Blue (MB) having $\text{pH} = 5.0 \pm 0.1$ and (ii) MB solution obtained after treatment with APM followed by exposure to dark, sun light or UV for 1 hour. Figures in the inset represent the original solution of MB (Bottle A) and filtrate of Bottle A obtained after treatment with APM followed by exposure to dark, sun light or UV for 1 hour (Bottle B-D) respectively.

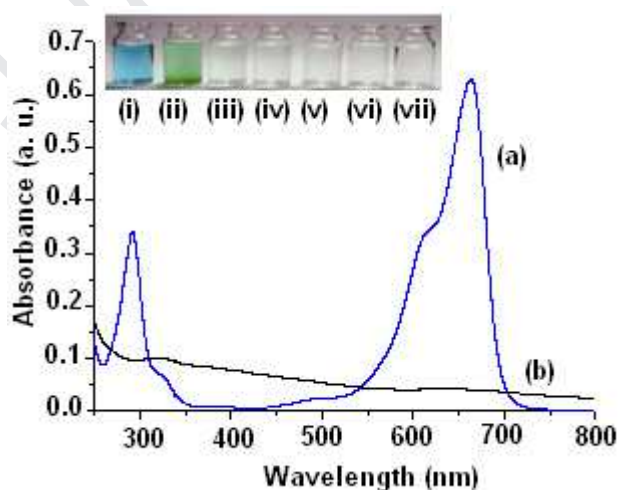


Figure 3. Figure in the inset shows the results obtained for time bound decolourization of MB ($\text{pH} = 5.0 \pm 0.1$).

(i) Original dye solution

(ii) Dye solution immediately after adding APM.

(iii)-(vii) Filtrate collected after 0, 15, 30, 45 and 60 minutes respectively.

(a) and (b) Represent the corresponding UV-Visible spectra of original MB solution i.e.

Bottle (i) and filtrate of Bottles (iii-vii) respectively.

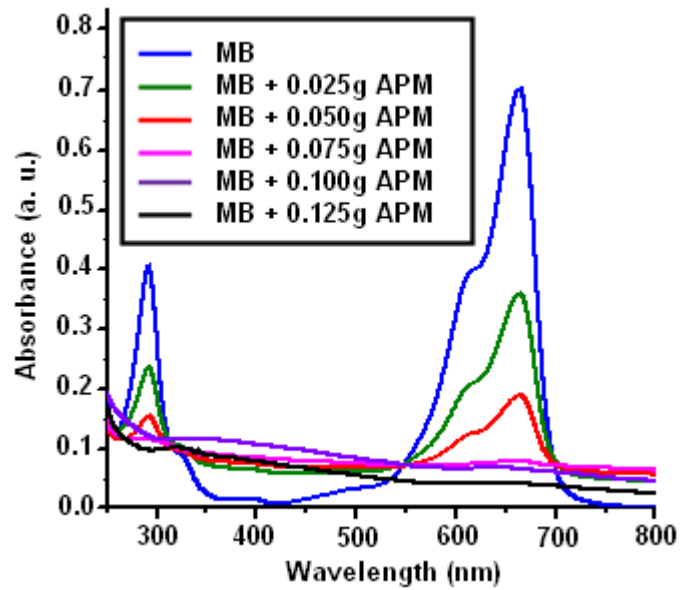


Figure 4. Figure showing the decrease in intensity of absorbance peak of MB solution ($\lambda_{\max} = 660$ nm) upon increasing the amount of APM.

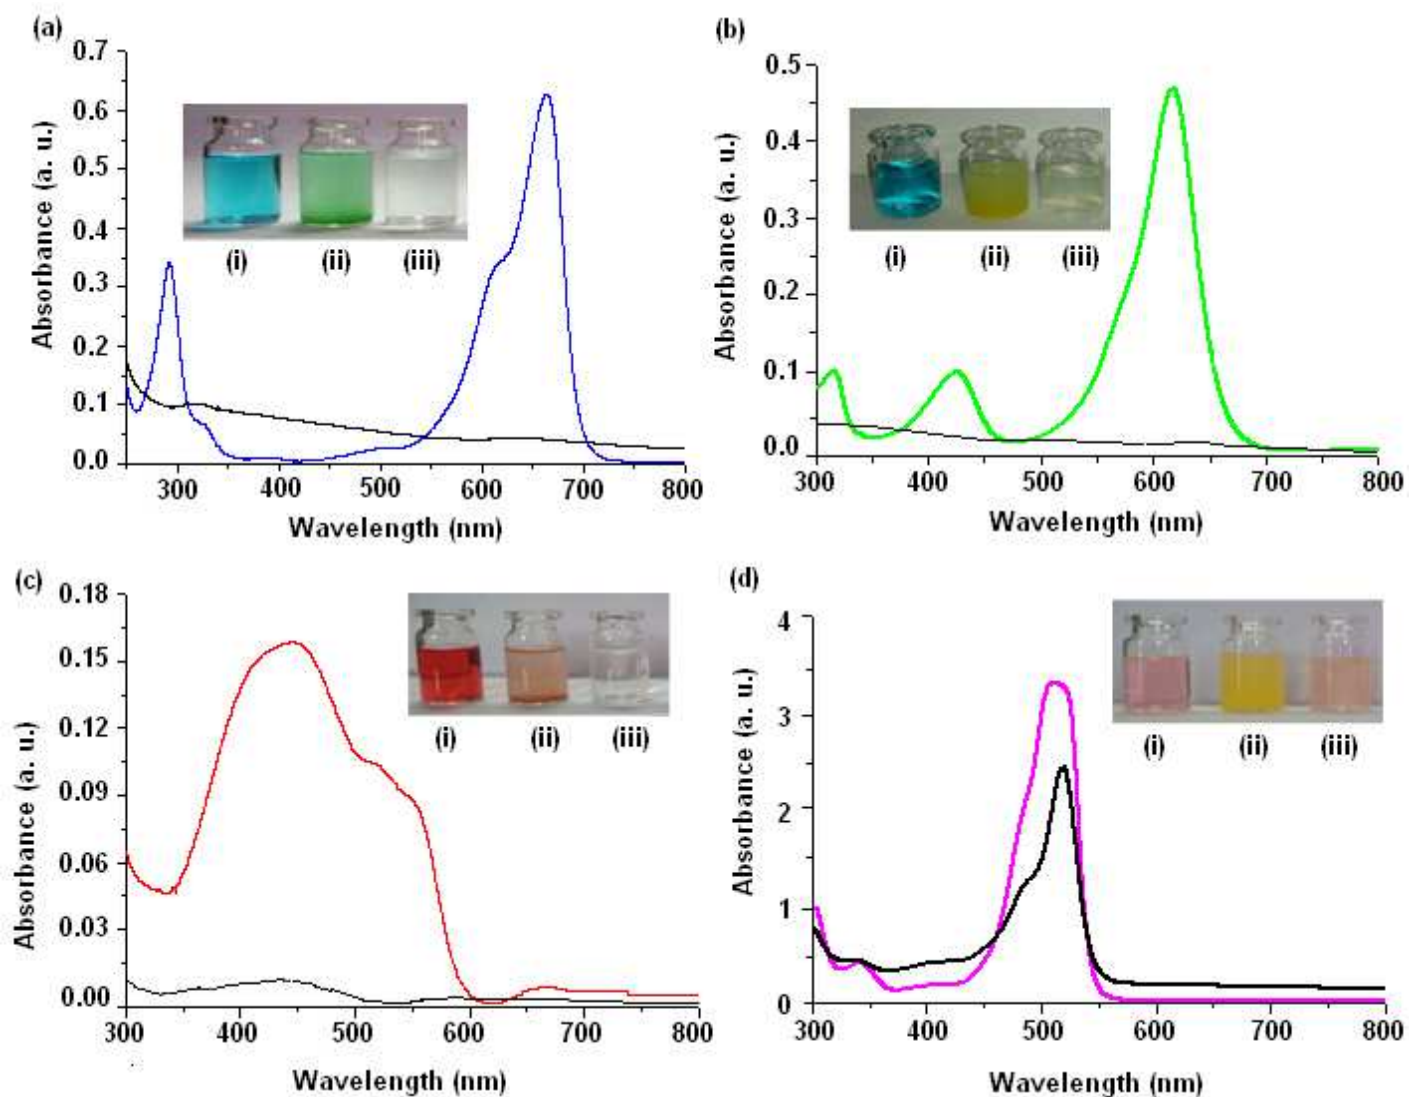


Figure 5. UV-Visible spectra of 25 mL of 10^{-5} M dye solution having $\text{pH} = 5.0 \pm 0.1$ of (a) MB (b) MG (c) MR and (d) EY before (coloured curve) and after (black curve) treatment with 0.125 g of APM.

Figure in the inset shows (i) original dye solution (ii) dye solution immediately after adding 0.125 g of APM (iii) filtrate of Bottle ii immediately after 5 minutes of stirring.

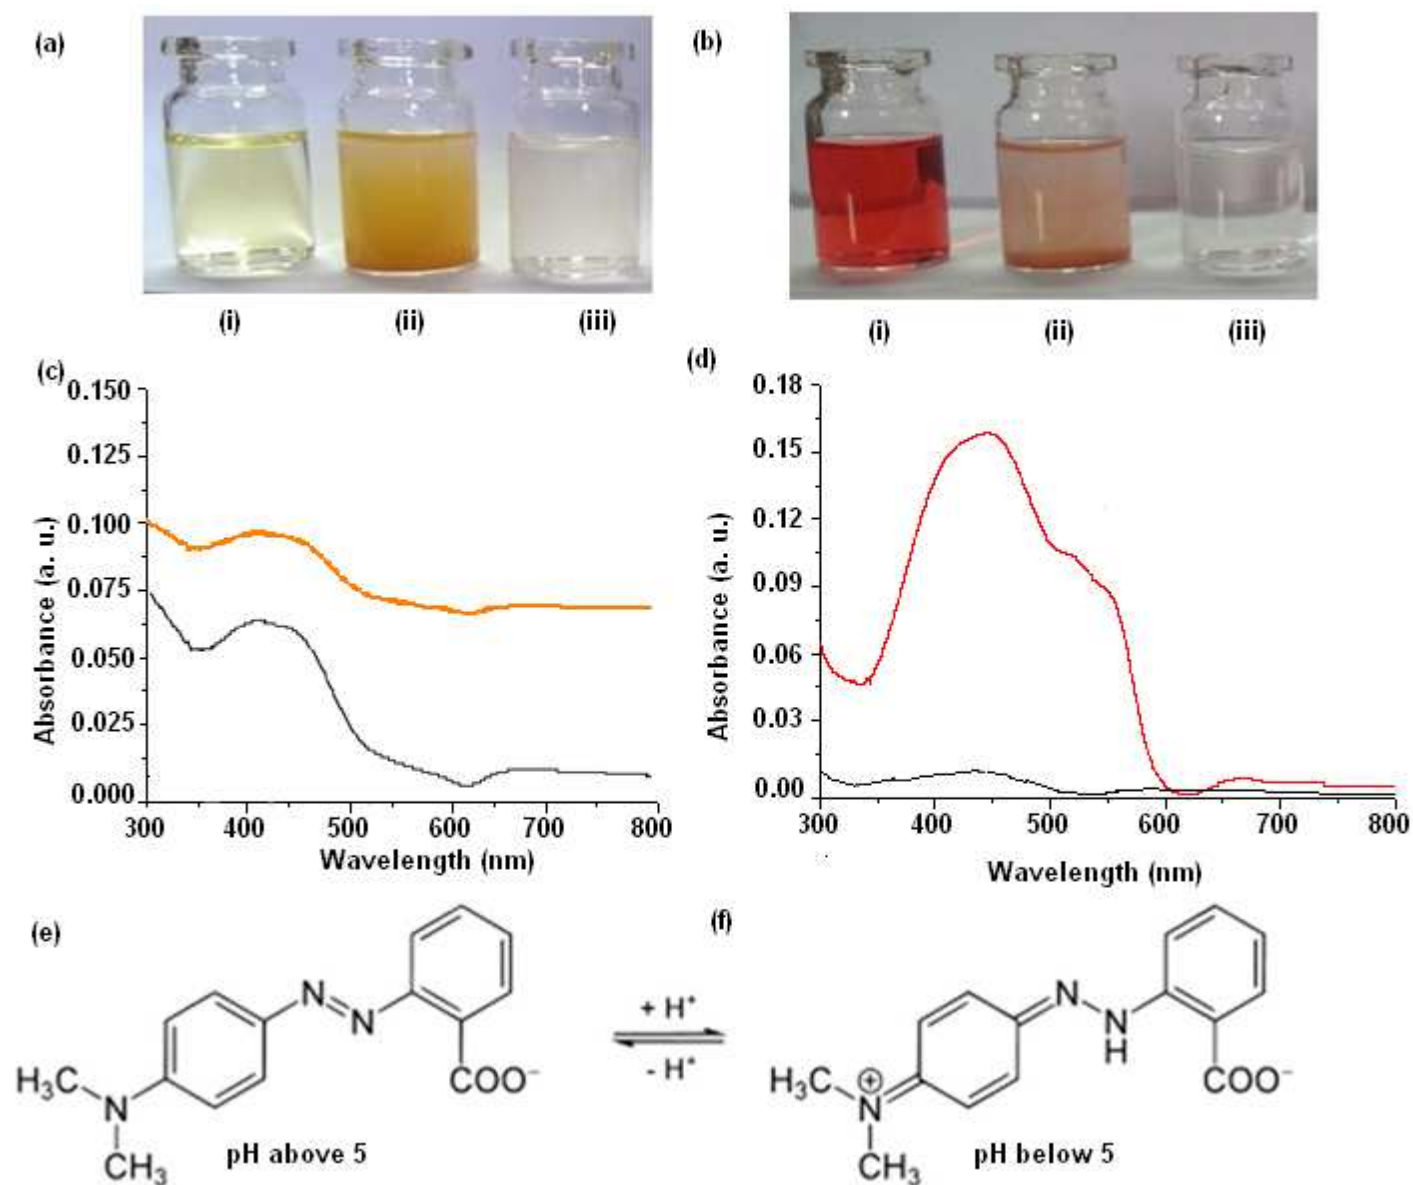


Figure 6. (a) and (b) Dye solutions of MR at pH above and below 5 respectively with (i) original dye solution (ii) dye solution immediately after adding 0.125 g of APM (iii) filtrate of bottle ii immediately after 5 minutes of stirring.

(c) and (d) UV-Visible spectra of dye solutions (i) and (iii) of MR shown in Figure 6a and 6b respectively.

(e) and (f) Structure of MR at pH above and below 5 respectively.

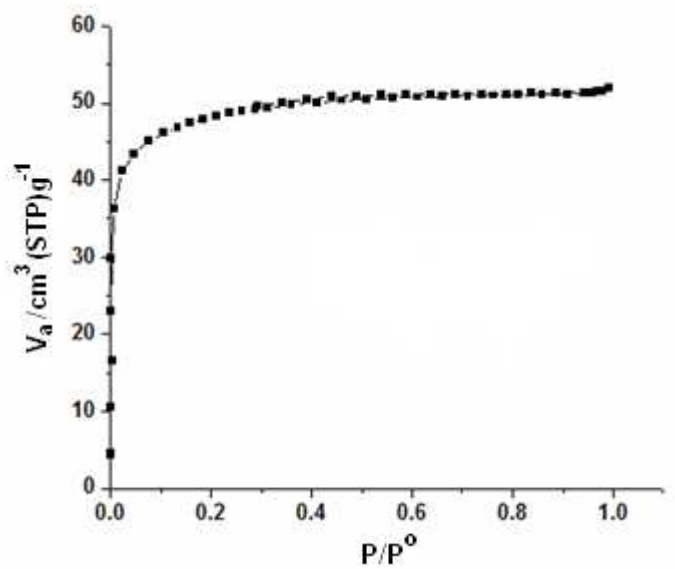


Figure 7. The adsorption/desorption isotherm of APM which resembles that of Brunauer's Type I isotherm.

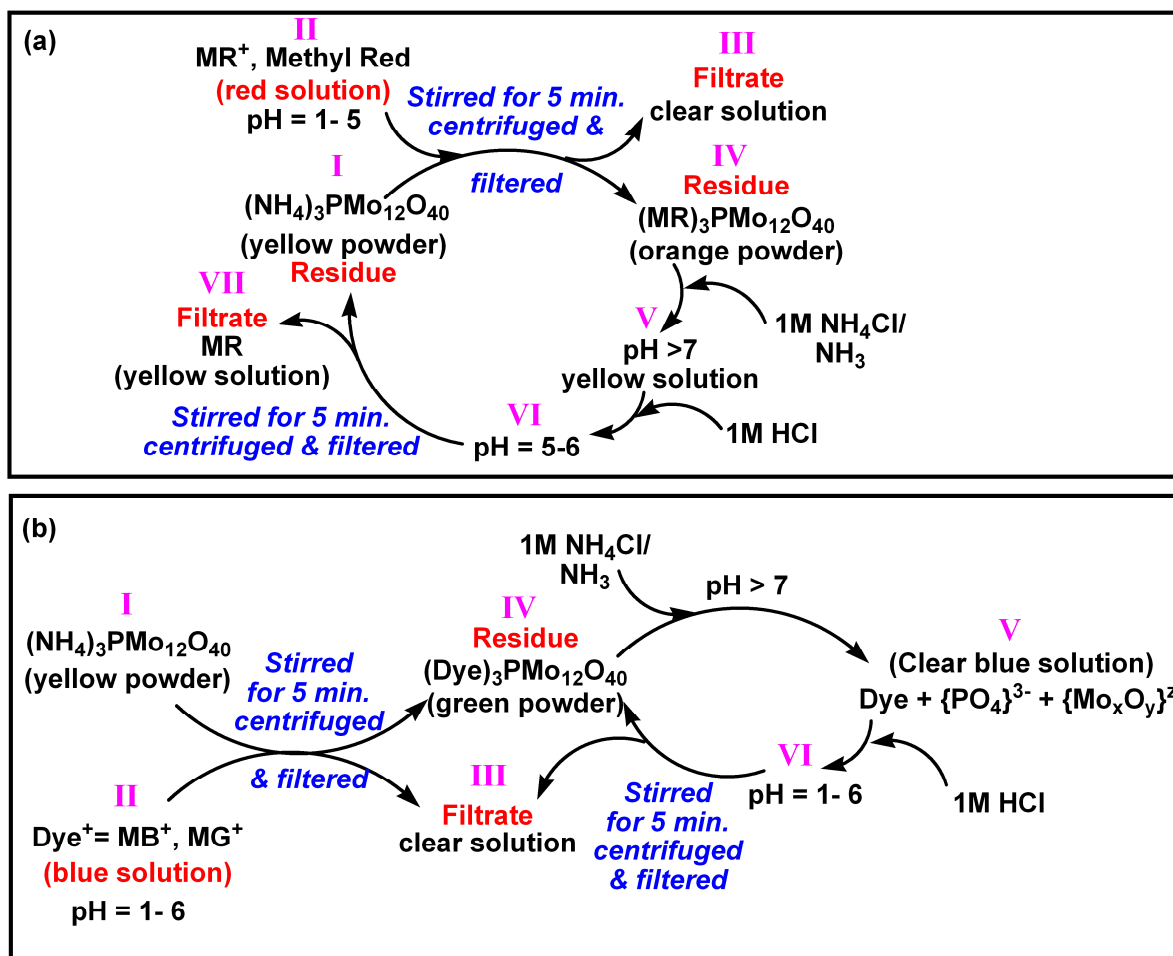


Figure 8. Release of ion-exchanged dye moieties in solution upon treatment with 1M NH_4Cl and NH_3 solution. (a) Ion-exchange mechanism for MR. (b) Ion-exchange mechanism for MB and MG.

Highlights

- Micro-sized ammonium phosphomolybdate (APM) particles synthesized and characterized.
- APM effectively removed cationic dyes from dye-contaminated water.
- Mechanism involved ion-exchange of NH_4^+ ions in APM with cationic dye moieties.
- APM retained its removal efficiency of 94.6% upto 16th cycle.
- Sensitivity to pH enabled APM to reverse the ion-exchange process.

Declaration of interests

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

The authors declare the following financial interests/personal relationships which may be considered as potential competing interests:

Declarations of interest: **None**

Journal Pre-proof